

Group	111 – PE/P/Q
Curing	min: 170°C @ 20' to 40' max: 200°C @ 08' to 12'
Surface	Smooth
Gloss	75-90 @60°
Approvals	Qualicoat: P-0554 GSB : Florida 1 Quality (152 g) EN 12206-1:2021 MED

PRODUCT DESCRIPTION

A gloss TGIC-free thermosetting polyester powder coating featuring excellent resistance to UV radiation and outdoor weathering. The product forms a protective and decorative film with enhanced outdoor resistance.

PE/P/Q is designed to protect aluminum and galvanized steel components used in the fenestration industry and carry GSB (I.152g) and Qualicoat class 1 category 3 (license P-0554) certification

Typical applications are door, window and cladding installations on domestic and commercial buildings.

Advantages:

- RAL colors on stock
- Excellent outdoor durability
- Qualicoat and GSB approved

Storage Life

Store the product between 5 and 30°C
Use within: 24 months

CHARACTERISTICS

Spec. Gravity (kg/l): 1,4 – 1,5
DFT (micron): 60 - 80
Theoretical Coverage @60um: 11 m²/kg

Recommended film thickness:
Dry: 60 - 80 µm


Reaction To Fire EN 13501-1
Classification: A2-s1, d0

APPLICATION

Suitable for automatic and manual electrostatic application
Please contact your Sherwin-Williams representative to discuss tribo-static application

Curing:

Time	Substrate temperature
8-12 min	200°C
10-20 min	190°C
15-25 min	180°C
20-40 min	170°C

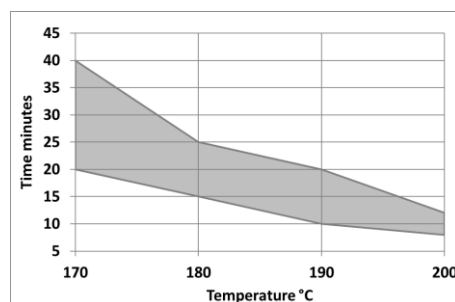

CHEMICAL RESISTANCE

Immersion testing for 48 hours at ambient temperature:
Chemical Effect
hydrochloric acid 10 % No change
Nitric acid 30 % matt, but washing off
Sulphuric acid 10% No change
hydrogen peroxide 40 v v No change
ammonium hydroxide 10% No change
ammonium hydroxide 33 % No change
sodium hydroxide 5% No change
tartaric acid 5% No change
citric acid 5% No change
lactic acid 5% No change
ethanol No change
N-butanol No change
petroleum ether slightly softened

SUBSTRATE PREPARATION

The surface treatment should be chosen according to the type of substrate and the required performance.

The surface to be coated must be free from oxidation, oil, grease or any other form of contamination.

A good quality pretreatment process is recommended for optimum performance, certified products can be found via Qualicoat, GSB or Qualisteelcoat.

Final user should select the proper pretreatment based on corrosion resistance performance.

Where required, the corrosion resistance can be enhanced using a primer system.

Pretreatment	Substrate			
	Aluminum	Steel	Galvanized Steel	Metallized Steel
Chemical	Cr-free (Zr, Ti, Oxilanes or alternatives)	✓		✓
	Pre-anodising	✓		
	Chromate	✓		✓
	Phospho-chromate	✓		
	Iron phosphate		✓	
	Zinc phosphate		✓	✓
	Nano-ceramic		✓	
Mechanical	Sand blasting		✓	
	Soft blasting			✓
	Sweeping			✓

PERFORMANCE DATA

A coated aluminum panel (ALQ-36), DFT 60µm, stoving 15' @ 190°C (pmt) satisfied the following requirements,

Buchholz indentation test:
more than 90
UNI EN ISO 2815

Erichsen cupping test (mm):
more than 5
UNI EN ISO 1520

Direct impact test (cm.Kg):
more than 25
ASTM D 2794; ISO 6272-2:2002

Reverse impact test(cm.kg):
more than 25
ASTM D 2794; ISO 6272-2:2002

Cylindrical mandrel size 5:
No cracking
UNI EN ISO 1519

Crosscut adhesion (2mm) (GT):
Class 0
UNI EN ISO 2409

Resistance to humidity:
(Humidity test) 1000 hours
no blistering, infiltration from the cross
of max 1mm
UNI EN ISO 6270-2:2005

Accelerated Weathering:
1000h Xenon-arc
≥ 50% gloss retention
According with Qualicoat cycle
(ISO16474-2)

300h UV-B:
≥ 50% gloss retention
According with GSB cycle (ISO16474-3)

CAUTION

FOR INDUSTRIAL SHOP APPLICATION

Thoroughly review product label and Safety Data Sheet (SDS) prior to using this product.

A Safety Data Sheet is available from your local Sherwin-Williams facility or distributor

Note: Product Data Sheets are periodically updated to reflect new information relating to the product. It is important that the user obtain the most recent Product Data Sheet for the product being used. The information, rating, and opinions stated here pertain to the material currently offered and represent the results of tests believed to be reliable. However, due to variations in user handling and methods of application which are not known or under our control, The Sherwin-Williams Company cannot make any warranties as to the end result.